

Reusing copper alloy wastes to improve fracture toughness of epoxy

N.J. Abdulkader¹, P.S. Ahmed^{2,*}, A.A.K. Mohammed³ and B.M. Fadhil⁴

¹Department of Materials Engineering/University of Technology, Baghdad, Iraq

²Manufacturing & Industrial Engineering Dept., Faculty of Engineering, Koya University, Koya KOY45, Kurdistan Region, Iraq

³Department of Technical Mechanical and Energy Engineering, Erbil Technical Engineering College, Erbil Polytechnic University, Erbil, Iraq

⁴Department of Automotive Technology, Erbil Technology College, Erbil Polytechnic University, Erbil, Iraq

*Corresponding author: payman.suhbat@koyauniversity.org

ABSTRACT In this work, a manufacturing waste is used as a reinforcement material for the epoxy to improve the fracture toughness, where the copper alloy machining chip is used with different weight fractions 5, 10, 15, and 20 wt. % and each percentage are added with three-chip lengths 0.6, 0.8, and 1.18 mm. Three-point bending test of the notched sample is used to test crack behaviour in addition to using materials characterization techniques to show the effect of the chip on structure, bonding, glass transition temperature (T_g), reinforcement dispersion, and fracture surface of the epoxy. Results show that adding the machining waste chips can enhance crack behaviour, and it is greatly dependent on the amount and size of the chip. The novelty of this research is in adding 20 wt. % - 0.8 mm length of copper alloy chips which improves the glass transition temperature and changes the fracture surface from brittle to ductile.

KEYWORDS Machining chip; fracture toughness; Stress intensity factor; Composites materials

1. Introduction

The two main ways that society engages with the environment are as a provider of natural resources and as a repository for solid, gaseous, and liquid pollution (Fratila and Davim, 2013). People have become more consumerist as a result of population increase and technological advancements, which has had detrimental consequences on the environment such as mineral consumption, energy production, and waste production (Batista et al., 2021). Millions of metric tons of steel, coal, aluminum, and cobalt are used in global production. Recycling the waste from these metals can improve economic value while reducing environmental harm (Zhai and Yuan, 2012). As a result, numerous studies evaluated the reuse of metal chips in various applications, such as the use of steel chips as reinforcement in metal matrices (Yao et al., 2016) or the use of metal chips to sinter powder mixtures to create porous structures instead of using sand in the production of concrete (Alwaeli and Nadziakiewicz, 2012; Alaneme and Odoni, 2016; Gecu and Karaaslan, 2020). The strength of the densified product depends on the bonding between the matrix and the chips or between the chips and the chips. Consequently, how the chips interact with the matrix determines whether these applications are successful. For instance, concrete chips could oxidize (Batista et al., 2021). These enhancements made by researchers can be used to enhance epoxy resin behaviour.

epoxy resins are a kind of high cross-link density ther-

moset polymers used in a variety of industries, such as adhesives, electronics, automotive, and aerospace. They function exceptionally well at high temperatures and have strong strength, high modulus, and little creep. Yet, the main problem when using epoxy is that it loses its fracture toughness and brittleness due to its high cross-link density, rendering it prone to crack initiation and propagation (Bajpai and Wetzel, 2019).

By increasing fracture toughness and adding stiff fillers, such as carbon nano reinforcement (Bajpai et al., 2016), titanium oxide (Carballeira and Haupert, 2010), aluminum oxide (Wetzel et al., 2006), glass particles (Lee, 2000), and silicon oxide (Hsieh et al., 2010a,b; Liang and Pearson, 2010), it is possible to increase the strength and modulus of epoxy without compromising the glass transition (Bajpai and Wetzel, 2019).

By using a simple maximum load failure criterion, material fracture toughness can be determined from load deflection curves seen during testing of notched flexural specimens (AL-Jeabory, 2009).

The main motivation of this research is to control the crack growth of epoxy by adding copper alloy chips with various percentages and lengths which will act as an obstacle against crack growth and retard crack propagation.

2. Materials and methods

The utilization of production wastes to increase epoxy's stress intensity factor and fracture toughness is covered in this section.

2.1 Materials

epoxy resin from Sika Company - Sikadur 52 base was used as a matrix, which is a low-viscosity liquid mixed with a hardener at a ratio of 2:1. Table 1 shows the matrix properties (Data sheet of Sikadur-52).

Table 1: Properties of epoxy matrix (provided by the supplier).

Compression Strength	Flexural Strength	Tension Strength	Modulus of Elasticity
53 N/mm ²	50 N/mm ²	25 N/mm ²	1.06 kN/mm ²

Table 2: Chemical composition of the chip.

Cu	58.489	Sb	0.396	Zr	0.063
Zn	37.381	Si	0.327	Ni	0.03
Pb	2.398	Nb	0.125	Co	0.016
Al	0.677	S	0.088	As	0.01

The machining chip is collected and cleaned from dirt and grease, and then screened to obtain the three required sizes 0.6, 0.8 and 1.18 mm. Oxford X- Supreme 8000 XRF analyser was used to determine the chemical composition of the chip, as listed in Table 2.

2.2 Methods

By adding machining chips with weight percentages of 5, 10, 15, and 20 wt. % as suggested by Nair et al. (2016) and Singha and Thakur (2008), with three different chip lengths added for each percentage (0.6, 0.8, and 1.18 mm) as suggested by Abdullah and Hamad (2017) to improve the mechanical properties, and comparing the results to pure epoxy as a reference (Table 3), the flexural test was used to assess the impact of manufacturing waste on the epoxy. The optimal lengths and chip-to-epoxy ratio are then determined. The impact of the chip on the epoxy's structure, bonding, glass transition temperature (T_g), dispersion, and fracture surface was demonstrated using Fourier transform infrared spectroscopy (FTIR), X-ray Fluorescence (XRF), Differential Scanning Calorimeter (DSC), and Field Emission Scanning Electron Microscope (FESEM).

The chip was added to the resin–hardener mix of the epoxy and then to the moulds made from acrylics by hand layup method, where the composite mixture was added from one corner into the mould to avoid bubble formation. Subsequently, the mixture was stored to be cured at room temperature for 7 days (Fadhil et al., 2016). The moulds were cut and prepared for the three-point bending test.

FTIR test is performed according to ASTM E1252, which is developed by Bruker Optics Company, Germany; its type is TENSOR-27. FTIR was used to examine and characterise the surface of the prepared composites (ASTM E1252-98, 2002). It is equipped with a room temperature DTGS detector, mid-IR source 4000–400 cm⁻¹ and a KBr beam splitter.

DSC device (Perkin-Elmer Corporation), type (Shimadzu-DSC-60) is used to check if the chip addition reduces the glass transition temperature of epoxy or improve its performance. Samples with a 10 mg mass were inserted in the holder along with a normal 40 µL aluminium crucible for the DSC test. As a reference holder, a different empty aluminium crucible of the same weight

Table 3: Percentage and size of reinforcements used in this study.

Specimen No.	Reinforce-ment %	Size (mm)	Specimen No.	Reinforce-ment %	Size (mm)
1	0	–	8	15	1.18
2	5	1.18	9	15	0.6
3	5	0.6	10	15	0.8
4	5	0.8	11	20	1.18
5	10	1.18	12	20	0.6
6	10	0.6	13	20	0.8
7	10	0.8			

was 7 because a heater and a temperature sensor were included with each holder. The test was performed on samples, and each sample was heated at a range starting from -160 °C until 60 °C with a rate of 0 °C/min prior to cooling to room temperature.

FESEM-MIRA 3 LMU, MI 18112751Q was used to determine the chip dispersion and the behaviour of crack surface, whether it is brittle or improved, to show some ductility.

2.3 Fracture toughness test

A sample's resistance to fracture can be determined by fracture toughness. To gauge the fracture toughness of a sample put through the single-edge notched bending SENB test, the force applied to the movable center pin of the three-point bending test apparatus at the critical point should be measured. The critical point of a SENB test is defined as the maximum of the load-displacement curve, where an unstable fracture starts with increasing center pin displacement (Biswakarma et al., 2021). The fracture toughness, sometimes referred to as the critical stress intensity factor K_{IC} , is computed using Eq. 1 (ASTM D5045-14, 2014), as follows (Bajpai and Wetzel, 2019):

$$K_{IC} = \frac{P}{BW^{0.5}} f\left(\frac{a}{W}\right) \quad (1)$$

where P is the applied load at the critical point, B is the thickness of material, W is the width of the material, and a is the length of the crack. The crack length is supposed to remain constant up until the point of unstable fracture for materials that follow linear elastic fracture mechanics (LEFM). According to ASTM D5045-14 (2014), the function $f(a/W)$ is defined in Eq. 2 (Bajpai and Wetzel, 2019).

$$f\left(\frac{a}{W}\right) = f(\alpha) = \frac{(2 + \alpha)}{(1 - \alpha)^{3/2}} \times (0.866 + 4.64\alpha - 13.32\alpha^2 + 14.72\alpha^3 - 5.6\alpha^4) \quad (2)$$

Fracture toughness or the energy release rate G_{IC} can be calculated using Eq. 3, as follows (Bajpai and Wetzel, 2019):

$$G_{IC} = \frac{K_{IC}^2 (1 - \nu^2)}{E} \quad (3)$$

where the ν is the poisson's ratio, which is set to 0.35, and E is the young's modulus in GPa (Bajpai and Wetzel, 2019).

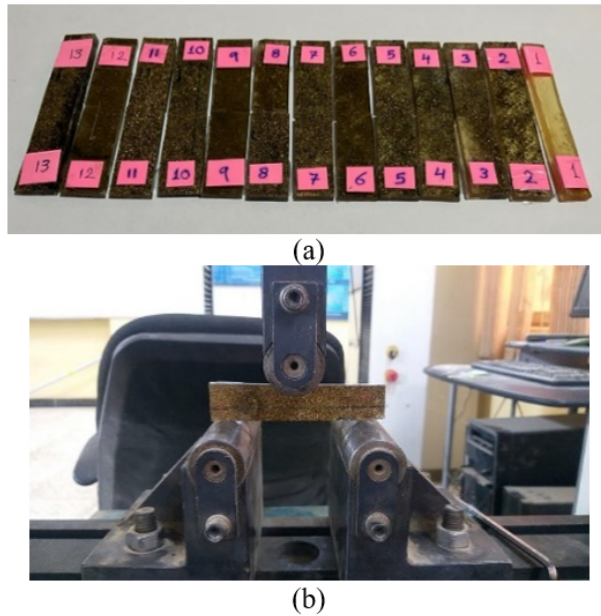


Figure 1: (a) Notched 3-point bending samples. (b) Universal bending test machine.

According to ASTM D5045-96 (1996), the three-point bending test was conducted to determine the material's fracture toughness and K_{IC} using fractured specimens with dimensions of 100 mm in length, 80 mm in span length, 20 mm in width, and 5 mm in thickness (Fig. 1).

3. Results and discussion

This section explains the results and discussion of three-point bending test of notched in addition to DSC, FTIR, XRF and SEM test.

The FTIR curves of all composites are comparable to that of epoxy, indicating that no new phases were formed but the intensities of transmittance % were increased for almost all samples compared with that of epoxy which indicates a good physical bonding (Salih et al., 2018).

Figure 2 shows the FTIR spectra of 5 % reinforcement. The Figure also shows that the intensity of the spectrum is increased compared with the epoxy spectrum because of the added chips.

The intensity of O–H stretching on the length of 0.6 mm is increased to less than 0.8 and 1.18 mm on 3400 cm^{-1} . Thus, the 0.6 mm length has less effect due to its shorter length because of the smaller bonding area between the chip and the epoxy.

Moreover, the intensity of C–H stretching on 3000 cm^{-1} is increased for all added chips length. C=C stretching of the aromatic ring and N–H bending of primary amine on 1612 cm^{-1} are unaffected by any chip length.

A slight increase is found in the intensity of N–H bending of primary amine, C–C stretching of the aromatic ring, C–N stretching of imide, C–O–C stretching in ether linkage and C–H out of plane of the aromatic ring at 1570 , 1512 , 1384 , 1035 and $750\text{--}572\text{ cm}^{-1}$, respectively, in all chips lengths (Ramírez Herrera et al., 2021).

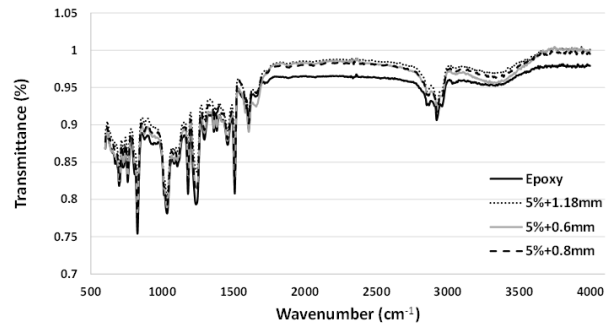


Figure 2: FTIR curves of 5 % reinforced epoxy with 0.6, 0.8 and 1.18 mm length.

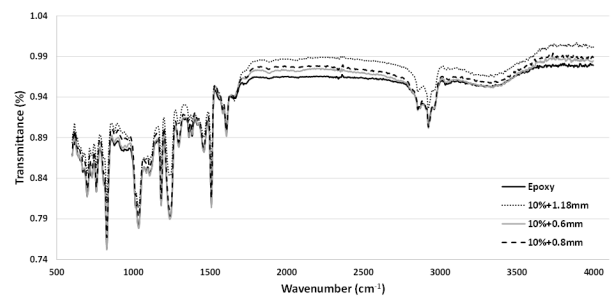


Figure 3: FTIR curves of 10 % reinforced epoxy with 0.6, 0.8 and 1.18 mm length.

Figure 3 shows the FTIR spectra of 10 % reinforcement. The figure shows that the intensity of O–H stretching and C–H stretching on the length of 1.18 mm is increased by more than 0.6 and 0.8 mm on 3400 and 3000 cm^{-1} , respectively, compared with epoxy resin due to its longer length because of the larger bonding area between the chip and the epoxy. Thus, the 1.18 mm length has a higher effect. C=C stretching of the aromatic ring and N–H bending of the primary amine on 1612 cm^{-1} are unaffected by any chip length. A slight increase is found in the intensity of N–H bending of primary amine, C–C stretching of the aromatic ring, C–N stretching of imide, C–O–C stretching in ether linkage and C–H out of plane of the aromatic ring at 1570 , 1512 , 1384 , 1035 and $750\text{--}572\text{ cm}^{-1}$, respectively, in the 0.8 mm length. Moreover, a noticeable increase is achieved in the intensity of the same bonds when adding 1.18 mm length because to its length and the increased surface where the chip and epoxy are bonded, but adding 0.6 mm length does not affect the intensity of these bonds.

Figure 4 shows the FTIR spectra of 15 % reinforcement. This figure shows that the intensity of O–H stretching on 3400 cm^{-1} is the same for 0.8 mm length as that of epoxy, but it is higher with the addition of 0.6 mm length, much higher with a shift in the bond when added by 1.18 mm length. Moreover, this bond widening and decrease indicates that some reactions, usually hydrogen bonding interaction, have occurred. In addition, the shift in the bond indicates a structural change. The C–H stretching on 3000 cm^{-1} for the lengths of 1.18 and 0.8 mm is the same as that of epoxy but it is higher when 0.6 mm length is added. A small increase in the intensity of C=C

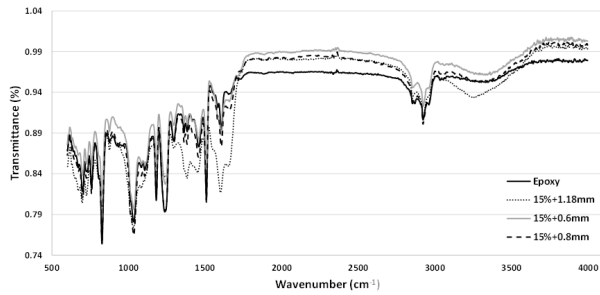


Figure 4: FTIR curves of 15 % reinforced epoxy with 0.6, 0.8 and 1.18 mm length.

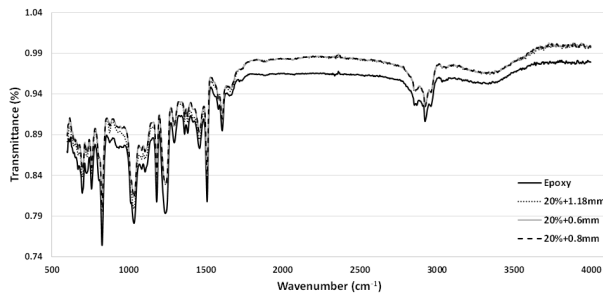


Figure 5: FTIR curves of 20 % reinforced epoxy with 0.6, 0.8 and 1.18 mm length.

stretching of the aromatic ring and N–H bending of primary amine on 1612 cm^{-1} is found when adding 0.6 and 0.8 mm lengths. However, bond widening and shifting are obtained when adding 1.18 mm length, attributed to the increase in bond strength and structural change, as shown in the stress intensity factor results. On 1399 cm^{-1} , the intensity of C–N–C stretching of the imide ring and C–N stretching of imide on 1384 cm^{-1} are increased 0.8 and 1.18 mm length, but it is the same for 0.6 mm as pure epoxy. Under 1232 cm^{-1} C–O–C stretching of ether linkage, the intensities are increased for 0.6 and 1.18 mm length but the same for 0.8 mm as pure epoxy. Under 1035 cm^{-1} C–O–C stretching of ether linkage and $828\text{--}800\text{ cm}^{-1}$ H–C= out-of-plane bending of MI ring and 1–4 substituted aromatic ring, the intensities are the same as those of epoxy for all lengths of chip reinforcement. Under $750\text{--}572\text{ cm}^{-1}$ C–H out-of-plane of aromatic ring the intensities are the same for 0.6 and 0.8 mm length, but it decreased to 1.18 mm when compared with pure epoxy because to its length and the increased surface where the chip and epoxy are bonded.

Figure 5 shows the FTIR spectra of 20 % reinforcement. The figure shows that the intensity of O–H stretching on 3400 cm^{-1} , C–H stretching on 3000 cm^{-1} , C=C stretching of the aromatic ring and N–H bending of primary amine on 1612 cm^{-1} , N–H bending of primary amine with 1570 cm^{-1} length, C–C stretching of the aromatic ring on 1512 cm^{-1} and C–N stretching of imide on 1384 cm^{-1} increased with all lengths of the reinforcement chip. Under 1100 cm^{-1} of aromatic stretching, the intensity is the same when adding 0.6 mm length chip but it is increased when adding 0.8 and 1.18 mm length when compared with epoxy since it is longer and

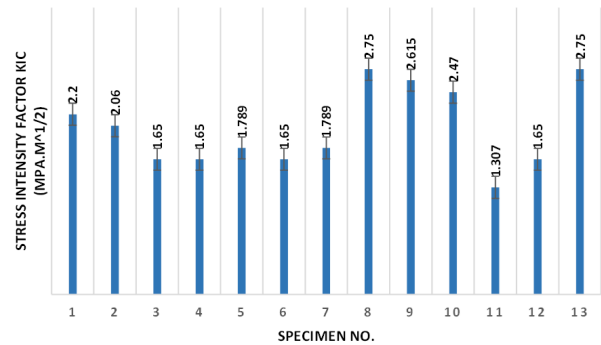


Figure 6: K_{IC} values of chip reinforced epoxy composites used in this study.

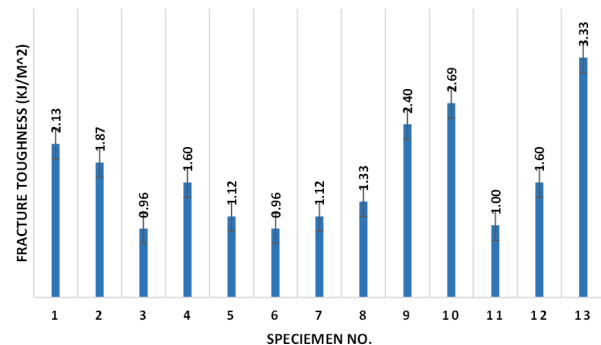


Figure 7: Fracture toughness (G_{IC}) values of chip reinforced epoxy composites used in this study.

has a larger surface area where the chip and epoxy are bonded. Under 1035 cm^{-1} C–O–C stretching of ether linkage, $828\text{--}800\text{ cm}^{-1}$ H–C= out-of-plane bending of MI ring and 1–4 substituted aromatic ring and $750\text{--}572\text{ cm}^{-1}$ C–H out-of-plane of aromatic ring, the intensities are the increased for all lengths of the chip reinforcement.

Figure 6 shows the stress intensity factor (K_{IC}) results. The 5 % and 10 % reinforcements decrease the K_{IC} of epoxy at all reinforcement lengths. This condition may be related to inhomogeneity caused by these percentages (Fadhil et al., 2016) in the epoxy structure, which acts as stress raiser. However, the 15 % reinforcement improves the stress intensity factor for all reinforcement lengths, where the K_{IC} increased from 2.2 to 2.75, at 2.615 and 2.47 MPa·m^{1/2} for 1.18, 0.8 and 0.6 mm reinforcements. This improvement is related to crack pinning (Domun et al., 2017), which occurs when the reinforcement amount is sufficiently high to act as an obstacle against crack. Adding 20 % leads to the highest improvement in K_{IC} when the reinforcement is 0.6 mm in size. This finding is also related to the crack pinning, where the K_{IC} value increased to 2.75 MPa·m^{1/2} as in the case of 15 % with 1.18 mm length. However, using larger size of reinforcement to 0.8 and 1.18 mm leads to drawback in the K_{IC} value due to inefficient dispersion and ineffectual cross-linking (Domun et al., 2017).

The effect of reinforcement size and percentages on the fracture toughness (G_{IC}) (Fig. 7) is close to their effect on the K_{IC} except that in the case of sample no. 8

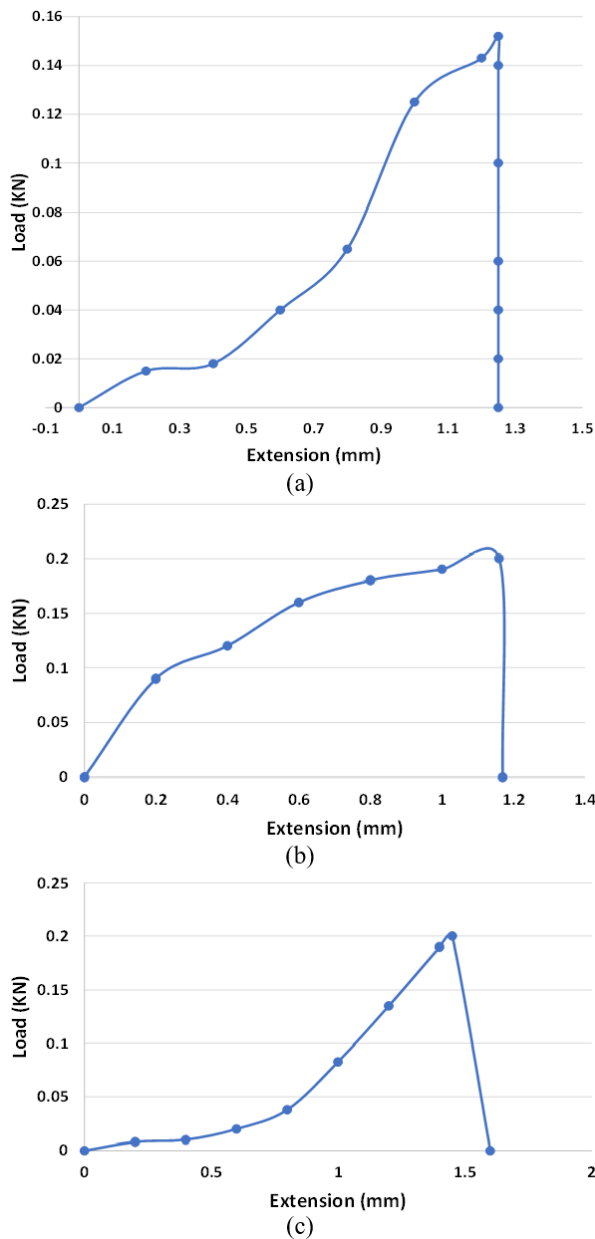


Figure 8: Load-extension curves of (a) epoxy, (b) sample no. 8 and (c) sample no. 13.

(15 % with 1.18 mm length), where the G_{IC} is reduced. Different from K_{IC} , this condition is due to the fact that the K_{IC} is dependent on the load, material dimension and design, as shown in Eq. 1, whereas the G_{IC} considers the material ductility and elongation in addition to the load and material design, as shown in Eq. 2.

Figure 8 shows the load extension curve of epoxy and samples no. 8 and 13. The figure shows that the extension of sample no. 8 (1.18 mm) is lower than that of epoxy (1.3 mm) and that of sample no. 13, despite the load of sample no. 8 (0.2 kN), is higher than that of epoxy (0.155 kN). This condition decreases the G_{IC} from 2.13 kJ/m² to 1.33 kJ/m², whereas the load (0.2 kN) and extension (1.6 mm) of sample no. 13 are higher than those of epoxy. Sample no. 13 is better than sample no. 8 because of its higher G_{IC} . The SEM images of the crack

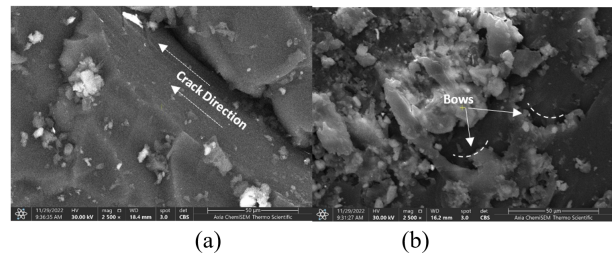


Figure 9: SEM image of (a) epoxy at 2500x, (b) sample no. 13 at 2500x.

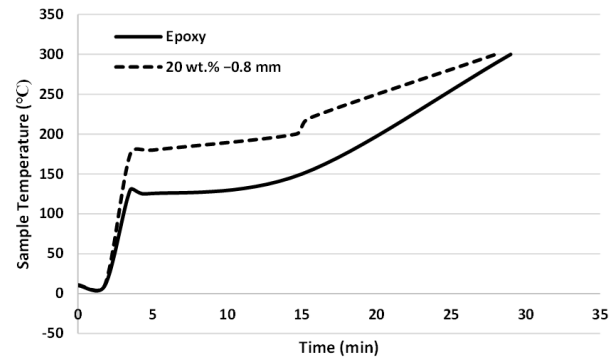


Figure 10: Glass transition temperature of epoxy resin and epoxy with 20 wt. % - 0.8 mm length of chip.

surface of epoxy and sample no. 13 are shown in Fig. 9. The change in crack behaviour from smooth and brittle for epoxy surface in the form of straight directions (which means when the crack initiated it will continue to grow fastly to fracture) Fig. 9a to ductile and rough-containing bows (which means when crack initiated, it will need time to grow to fracture where the chip will act as an obstacle against crack growth) Fig. 9b for sample no. 13 surface is evident, indicating the increase in the G_{IC} of sample no. 13.

The effect of adding 20 wt. % - 0.8 mm length of chip on the glass transition temperature (T_g) of epoxy is shown in Fig. 10. The figure shows that the addition of chip highly changed the glass transition temperature (T_g), where its value is increased from 150 °C to 200 °C. The increase in T_g is most likely attributable to a decrease in the mobility of epoxy resin chain segments as a result of the Cu-Zn chip/matrix interactions (Lu et al., 2007) which is another evident on increasing the strength.

4. Conclusions

In this work, a manufacturing waste is used as a reinforcement material for epoxy to improve the fracture toughness and the stress intensity factor. The machining chip is used with different weight fractions and three different lengths. The result shows that adding the machining wastes in the form of chips can enhance crack behaviour and the performance is greatly dependent on the amount and size of the chip. Moreover, adding 20 wt. % - 0.8 mm length of copper alloy chips which changes the glass transition temperature and change the fracture surface from brittle to ductile, thereby reducing the velocity of crack growth

due to its good physical bonding and the larger bonding area between the chip and the epoxy.

References

- Abdullah, S. and Hamad, G. (2017). *Study the effect of adding low weight percentage of Brass chips on the me-mechanical properties of Epoxy. Graduation project.* Erbil Polytechnic University, Kurdistan region, Iraq.
- AL-Jeabory, J. (2009). The J- integral and K_{IC} as a measure of fracture toughness of steel fibre concrete. *The Iraqi Journal for Mechanical and Material Engineering. Iraqi J. Mech. Mater. Eng.*, C:386–398.
- Alaneme, K. K. and Odoni, B. U. (2016). Mechanical properties, wear and corrosion behavior of copper matrix composites reinforced with steel machining chips. *Eng. Sci. Technol. an Int. J.*, 19(3):1593–1599.
- Alwaeli, M. and Nadziakiewicz, J. (2012). Recycling of scale and steel chips waste as a partial replacement of sand in concrete. *Constr. Build. Mater.*, 28(1):157–163.
- ASTM D5045-14 (2014). *Standard Test Methods for Plane-Strain Fracture Toughness and Strain Energy Release Rate of Plastic Materials.* ASTM International, West Conshohocken, PA, USA.
- ASTM D5045-96 (1996). *Standard Test Method for Plane-Strain Fracture Toughness and Strain Energy Release Rate of Plastic Materials.* American Society for Testing and Materials, Philadelphia, USA.
- ASTM E1252-98 (2002). Standard Practice for General techniques for Obtaining Infrared Spectra for Qualitative Analysis. *Annu. B. ASTM Stand.*, E 1252-98:1–11.
- Bajpai and Wetzel (2019). Effect of different types of block copolymers on morphology, mechanical properties, and fracture mechanisms of bisphenol-F based epoxy system. *J. Compos. Sci.*, 3(3):68.
- Bajpai, A., Alapati, A. K., and Wetzel, B. (2016). Toughening and mechanical properties of epoxy modified with block co-polymers and MWCNTs. *Procedia Struct. Integr.*, 2:104–111.
- Batista, C. D., Fernandes, A. A. M. d. N. d. P., Vieira, M. T. F., and Emadinia, O. (2021). From machining chips to raw material for powder metallurgy. A review. *Materials (Basel)*, 14(18):5432.
- Biswakarma, J. J. S., Cruz, D. A., Bain, E. D., Dennis, J. M., Andzelm, J. W., and Lustig, S. R. (2021). Modeling brittle fractures in epoxy nanocomposites using extended finite element and cohesive zone surface methods. *Polymers (Basel)*, 13(19):3387.
- Carballeira, P. and Haupert, F. (2010). Toughening effects of titanium dioxide nanoparticles on TiO₂/epoxy resin nanocomposites. *Polym. Compos.*, 31(7):1241–1246.
- Domun, N., Hadavinia, H., Zhang, T., Liaghat, G., Vahid, S., Spacie, C., Paton, K. R., and Sainsbury, T. (2017). Improving the fracture toughness properties of epoxy using graphene nanoplatelets at low filler content. *Nanocomposites*, 3(3):85–96.
- Fadhil, B. M., Ahmed, P. S., and Kamal, A. A. (2016). Improving mechanical properties of epoxy by adding multi-wall carbon nanotube. *J. Theor. Appl. Mech.*, page 551.
- Fratila, D. and Davim, J. P. (2013). *Green Manufacturing Processes and Systems.* Materials Forming, Machining and Tribology. Springer, Berlin, Heidelberg.
- Gecu, R. and Karaaslan, A. (2020). Casting temperature dependent wear and corrosion behavior of 304 stainless steel reinforced A356 aluminium matrix bimetal composites fabricated by vacuum-assisted melt infiltration casting. *Wear*, 446-447:203183.
- Hsieh, T., Kinloch, A., Masania, K., Taylor, A., and Sprenger, S. (2010a). The mechanisms and mechanics of the toughening of epoxy polymers modified with silica nanoparticles. *Polymer (Guildf)*, 51(26):6284–6294.
- Hsieh, T. H., Kinloch, A. J., Masania, K., Sohn Lee, J., Taylor, A. C., and Sprenger, S. (2010b). The toughness of epoxy polymers and fibre composites modified with rubber microparticles and silica nanoparticles. *J. Mater. Sci.*, 45(5):1193–1210.
- Lee, J. (2000). Fracture of glass bead/epoxy composites: on micro-mechanical deformations. *Polymer (Guildf)*, 41(23):8363–8373.
- Liang, Y. and Pearson, R. (2010). The toughening mechanism in hybrid epoxy-silica-rubber nanocomposites (HESRNs). *Polymer (Guildf)*, 51(21):4880–4890.
- Lu, S.-R., Wei, C., Yu, J.-H., Yang, X.-W., and Jiang, Y.-M. (2007). Preparation and characterization of epoxy nanocomposites by using PEO-grafted silica particles as modifier. *J. Mater. Sci.*, 42(16):6708–6715.
- Nair, J., Augustine, A., and Davanageri, M. (2016). Wear characteristics and vibration analysis of shell powder filled glass fiber reinforced epoxy composite laminates. *Int. J. Res. Eng. Technol.*, 5(11):215–221.
- Ramírez Herrera, C. A., Cruz Cruz, I., Jiménez Cedeño, I. H., Martínez Romero, O., and Elías Zúñiga, A. (2021). Influence of the epoxy resin process parameters on the mechanical properties of produced bidirectional [±45°] carbon/epoxy woven composites. *Polymers (Basel)*, 13(8):1273.
- Salih, S. I., Oleiwi, J. K., and Ali, H. M. (2018). Study the mechanical properties of polymeric blends (SR/PMMA) using for maxillofacial prosthesis application. *IOP Conf. Ser. Mater. Sci. Eng.*, 454(012086).
- Singha, A. S. and Thakur, V. K. (2008). Mechanical properties of natural fibre reinforced polymer composites. *Bull. Mater. Sci.*, 31(5):791–799.
- Wetzel, B., Rosso, P., Haupert, F., and Friedrich, K. (2006). Epoxy nanocomposites - fracture and toughening mechanisms. *Eng. Fract. Mech.*, 73(16):2375–2398.
- Yao, B., Zhou, Z., Duan, L., and Xiao, Z. (2016). Compressibility of 304 stainless steel powder metallurgy materials reinforced with 304 short stainless steel fibers. *Materials (Basel)*, 9(3):1–11.
- Zhai, Q. and Yuan, C. (2012). Separating manufacturing metal chips for recycling through a combined hydrodynamic and electromagnetic approach. In *Leveraging Technol. a Sustain. World*, pages 167–172. Springer, Berlin, Heidelberg.